

ASPHALT BINDER

Section 2 – Asphalt Performance Grading

Section 2 - 1


Grading of Asphalt Binder

- Viscosity of original
- Viscosity of aged asphalt
- Penetration of original
- SHRP performance grading

Section 2 - 2

Old Asphalt Testing Equipment

Penetration
AASHTO T 49, ASTM D 5

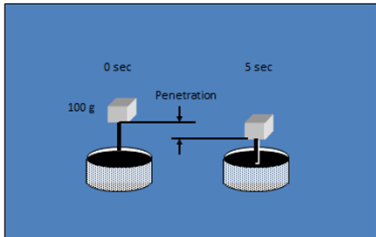

Section 2 - 3

Old Asphalt Testing Equipment

Absolute Viscosity

The Asphalt Institute

Section 2 - 4

Old Asphalt Testing Equipment

Kinematic Viscosity

The Asphalt Institute

Section 2 - 5

Old Asphalt Testing Equipment

Cleveland Open Cup

Section 2 - 6

Old Asphalt Testing Equipment

Ductility

AASHTO T 51, ASTM D 113


- Ability of the asphalt binder to deform without breaking
- 5 cm/s at 25°C
- Some interpret low ductility to indicate brittle asphalt binders

Section 2 - 7

Performance Grading (PG) Asphalt Testing Equipment

Equipment	Purpose	Performance Property
Rotational Viscometer	Handling pumping	Flow
Rolling Thin Film Oven Test Pressure Aging Vessel	Simulate aging through Hot Plant Simulate long term aging	n/a
Dynamic Shear Rheometer	Measure properties @ high & intermediate temperature	Permanent deformation & fatigue cracking
Bending Beam Rheometer Direct Tension Tester	Measure properties @ low temperature	Low temperature cracking

Section 2 - 8

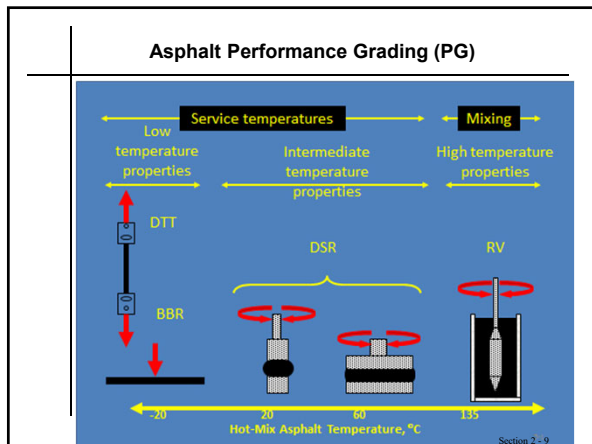


PG Asphalt Tests (Aging)

- **Rolling Thin Film Oven (RTFO):** It simulates the condition of asphalt immediately after construction
- **Pressure Aging Vessel (PAV):** It simulates the aging of asphalt after years of being in service. PAV samples must be RTFO aged first

Section 2 - 10

PG Asphalt Testing Equipment


Rolling Thin Film Oven (RTFO)

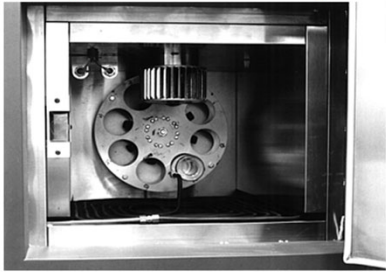

Section 2 - 11

PG Asphalt Testing Equipment

Rolling Thin Film Oven Sample Bottles

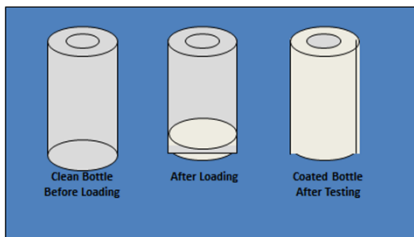


Section 2 - 12

PGAsphalt Testing Equipment

Pressure Aging Vessel (PAV)

AASHTO PP1

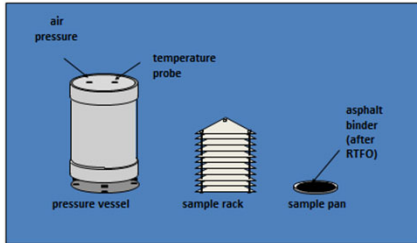

Section 2 - 13

PG Asphalt Testing Equipment

PAV



Section 2 - 14


PG Asphalt Tests (Rotational Viscometer)

- RV measures the viscosity of asphalt or tank asphalt at 135°C
- RV is used to determine if the asphalt is fluid enough to handle
- RV is performed on unaged asphalt only

Section 2 - 15

PG Asphalt Testing Equipment

Rotational Viscometer

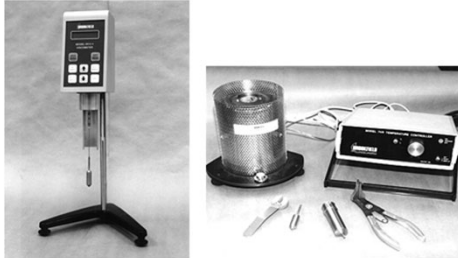

Section 2 - 16


PG Asphalt Tests (Dynamic Shear Rheometer)

- DSR is performed to check rutting and fatigue cracking
- DSR is used to characterize the viscous and elastic behavior of asphalt
- DSR measures the complex shear modulus (G^*) and phase angle (δ)
- DSR is performed on original, RTFO aged binder, and PAV aged binder

Section 2 - 17

PG Asphalt Testing Equipment

DSR

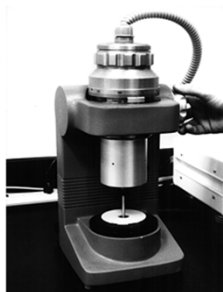

Section 2 - 18

PG Asphalt Tests (Bending Beam Rheometer)

- BBR is performed to check low temperature cracking
- BBR measures stiffness at very low temperatures
- BBR measures asphalt deflection under a constant load at a constant temperature. Parameters determined are stiffness (s) and slope (m)
- BBR is performed on PAV aged asphalt


Section 2 - 19

PG Asphalt Testing Equipment

Bending Beam Rheometer

AASHTO TP1


Evaluate low temperature creep stiffness of the asphalt binder

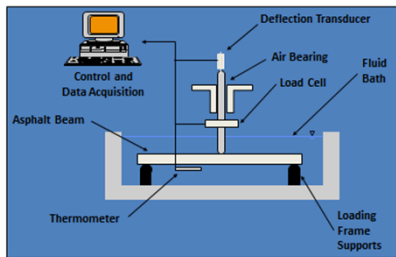

Section 2 - 20

PG Asphalt Testing Equipment

BBR Specimen Mold

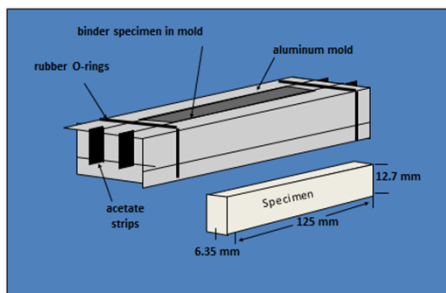

Section 2 - 21


PG Asphalt Tests (Direct Tension Tester)

- DTT is performed to check low temperature cracking
- DTT supplements the BBR
- DTT is not used in specification compliance
- DTT is performed on PAV aged asphalt

Section 2 - 22

PG Asphalt Testing Equipment

Direct Tension Test

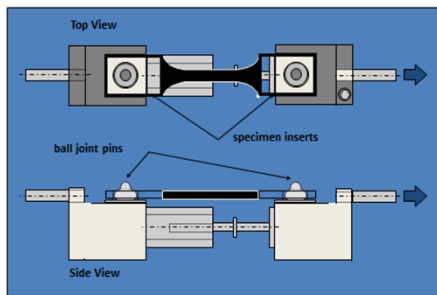


Section 2 - 23

Asphalt Performance Grading (PG)

- The main objective of PG is to improve field performance by limiting the potential of asphalt to contribute toward rutting, fatigue cracking, and low temperature cracking
- Physical properties are constant but the testing temperatures are different

Section 2 - 24

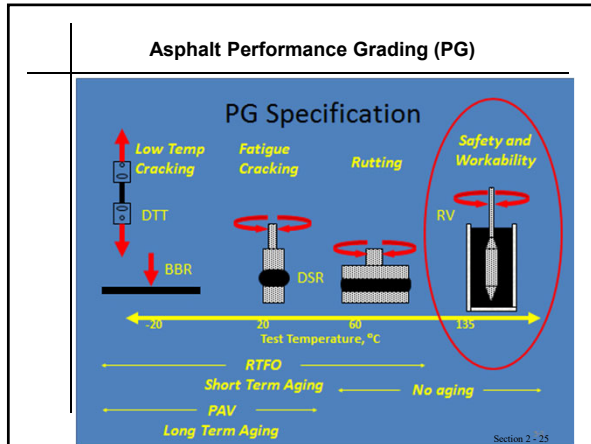

Asphalt Performance Grading (PG)

- The required PG grading for a specific location can be determined based on high and low pavement temperature
- High pavement temperature is calculated at a .8" (20 mm) depth based on seven-day average high air temperature and the geographic latitude of the project
- Low pavement surface temperature is determined based on the one-day minimum air temperature

Section 2 - 26

Asphalt Performance Grading (PG)

- The reliability concept is used to determine a degree of design risk to high and low temperatures
- Reliability levels range from 50 to 98 percent
- Current SHRP recommendations are to use 98% for the high traffic end and 50% for the low traffic end
- Air temperatures are available for thousands of weather stations nationwide

Section 2 - 27

Asphalt Performance Grading (PG)

- Seven grades are available based on high temperature (46, 52, 58, 64, 70, 76, and 82°C)
- Up to seven grades are available based on low pavement temperature [-10, -16, -22, -28, -34, -40, and -46°C]
- Examples: PG 52-22, PG 64-28
- Not all low temperatures are available with some high temperatures
- Deeper pavement layers may have lower grades

Section 2 - 28

Performance Grade Table

Performance Grade	PG 46				PG 52							
	-34	-40	-46	-10	-16	-22	-28	-34	-40	-46		
Average 7-day maximum Pavement Design temperature, °C	<=46				<=52							
Minimum Pavement Design temperature, °C	>=34	>=40	>=46	>=10	>=16	>=22	>=28	>=34	>=40	>=46		
Original Binder												
Flash Point 148g, 148: Minimum, °C	230											
Viscosity, ASTM D 4402: Maximum, 3 Pas (3000cP), Test, °C	135											
Dynamic Shear, TP3: G*mod, Minimum, 1.00 kPa Test Temperature @ 10min, °C	46				52							
Rolling Thin Film Oven (T 240) or Thin Film Oven (T 170) Residue												
Mass Loss, maximum, %	1.00											
Dynamic Shear, TP3: G*mod, Maximum, 2.20 kPa Test Temp @ 10min, °C	46				52							
Pressure Aging Vessel Residue (PAV)												
PAV Aging Temperature, °C	90				90							
Dynamic Shear, TP3: G*mod, Maximum, 2.20 kPa Test Temp @ 10min, °C	10	7	4	25	22	19	16	13	10	7		
Report												
Creep Stiffness, TP1: S, Maximum, 300 MPa or Minimum, 0.300 Test Temp, @ 60 sec, °C	-34	-30	-36	0	-6	-12	-18	-24	-30	-36		
Direct Tension, TP3: Failure Strain, Minimum, 1.00% Test Temp @ 1.0 min/min, °C	-24	-30	-36	0	-6	-12	-18	-24	-30	-36		

Section 2 - 29

Performance Grade Table

Performance Grade	PG 58				PG 64						
	-10	-22	-28	-34	-10	-16	-22	-28	-34	-40	
Average 7-day maximum Pavement Design temperature, °C	<=58				<=64						
Minimum Pavement Design temperature, °C	>=16	>=22	>=28	>=34	>=10	>=16	>=22	>=28	>=34	>=40	
Original Binder											
Flash Point Temp, 148: Minimum, °C	230										
Viscosity, ASTM D 4402: Maximum, 3 Pas (3000cP), Test, °C	135										
Dynamic Shear, TP3: G*mod, Minimum, 1.00 kPa Test Temperature @ 10min, °C	58				64						
Rolling Thin Film Oven (T 240) or Thin Film Oven (T 170) Residue											
Mass Loss, maximum, %	1.00										
Dynamic Shear, TP3: G*mod, Maximum, 2.20 kPa Test Temp @ 10min, °C	58				64						
Pressure Aging Vessel Residue (PAV)											
PAV Aging Temperature, °C	100				100						
Dynamic Shear, TP3: G*mod, Maximum, 2.20 kPa Test Temp @ 10min, °C	25	22	19	16	13	11	8	5	2	10	
Physical Hardening											
Creep Stiffness, TP1: S, Maximum, 300 MPa or Minimum, 0.300 Test Temp, @ 60 sec, °C	-6	-12	-18	-24	-30	0	-6	-12	-18	-24	
Direct Tension, TP3: Failure Strain, Minimum, 1.00% Test Temp @ 1.0 min/min, °C	-6	-12	-18	-24	-30	0	-6	-12	-18	-24	

Section 2 - 30

Performance Grade Table

Performance Grade	PG 70					PG 76					PG 82				
	-10	-16	-22	-28	-34	-10	-16	-22	-28	-34	-10	-16	-22	-28	-34
Average 7-day maximum Pavement Design temperature, °C	<70					<76					<82				
Minimum Pavement Design temperature, °C	>	>	>	>	>	>	>	>	>	>	>	>	>	>	>
Original Binder															
Flash Point Temp, T48, Minimum °C	230														
Viscosity, ASTM D 4402, Minimum, 3 Pas (30000P), 150, °C	135														
Dynamic Shear, TP3, G*Sinδ, Minimum, 1.00 MPa-Sinδ Temperature @ 10min, °C	70					76					82				
Rolling Thin Film Oven (RTFO) or Thin Film Oven (TFO) residue															
Mass Loss, Minimum, %	1.00														
Dynamic Shear, TP5, G*Sinδ, Minimum, 2.20 MPa-Sinδ Temp @ 10min, °C	70					76					82				
Pressure Aging Vessel Residue (PAV)															
PAV Aging Temperature, °C	100(110)					100(110)					100(110)				
Dynamic Shear, TP5, G*Sinδ, Minimum, 5000 MPa-Sinδ Temp @ 10min, °C	34	31	28	25	22	19	14	31	28	25	22	34	31	28	25
Physical Hardening															
Report															
Comp Diffusion, TP 1, Maximum, 200(100), min, Minimum, 0(200) Test Temp. @ 60min, °C	0	-6	-12	-18	-24	-30	0	-6	-12	-18	-24	0	-6	-12	-18
Direct Tension, TP3, Failure Strain, Minimum, 1.00% Test Temp @ 1.0 minute, °C	0	-6	-12	-18	-24	-30	0	-6	-12	-18	-24	0	-6	-12	-18

Section 2 - 31

Table: Asphalt Binder Grades and Reliability for Selected Cities (Asphalt Institute)

ST	Station	Latitude	Min 50% Grade	Actual Reliability		Min 98% Grade	Actual Reliability	
				High	Low		High	Low
FL	Miami WSCOMO AP	25.80	PG 58-10	99	99.9	PG 58-10	99	99.9
WY	Cheyenne WSFOAP	41.15	PG 52-22	68	55	PG 58-28	99.9	98.9
TX	Houston FAAAP	29.65	PG 64-10	99.9	99.3	PG 64-10	99.99	99.3
NY	New York Inter AP	40.65	PG 52-16	61	97.1	PG 58-16	99.9	97.1
CO	Denver WSFOAP	39.77	PG 58-22	99.9	78	PG 58-28	99.9	99
CA	Los Angeles WSOAP	33.93	PG 52-10	66	99.9	PG 58-10	99.9	99.9

Section 2 - 32

Asphalt Performance Grading (PG)

- > Cheyenne, Wyoming PG 52-22 @ 50 percent reliability
- > Cheyenne, Wyoming PG 58-28 @ 98 percent reliability
- > Miami Florida PG 58-10 @ 50 percent reliability
- > Miami Florida PG 58-10 @ 98 percent reliability
- > WYDOT uses LTPP-Bind for determination of appropriate grade for any particular layer.

Section 2 - 33

Example: Frontier PG64-22

Example: Frontier PG 64-22	PG 64					PG 70					
Performance Grade	-16	-22	-28	-34	-40	-16	-16	-22	-28	-34	-40
Digital binder											
Flash Point Temp. 148: Minimum, degrees C											
Rotational Viscosity: Maximum, 3 Pas (3000cP), Test Temp. 135, degrees C	0.701										
Dynamic Shear G* sin δ Minimum, 1.00 kPa Test Temp @ 10 rad/s, degrees C	64					7.0					
RTES: Residue	1.298 kPa					0.711 kPa					
Percent Change, 1.00 Max Loss	0.203										
Dynamic Shear G* sin δ Minimum 2.20 kPa Test Temp @ 10 rad/s, degrees C	42					7.0					
PAV Aging 20 hours @ 2.07 Mpa	100					100 / (115)					
Dynamic Shear TPS: G* sin δ Maximum, 5000 kPa Test Temp @ 10 rad/sec, degrees C	28	25	22	19	16	34	31	28	25	22	19
Creep Stiffness S, Maximum, 300 Mpa stiffness Test Temp @ 60 sec, degrees C m_value, Min 0.300 m_value	-6	-12	-18	-24	-30	0	-6	-12	-18	-24	-30
Physical Hardening											
24 Hours Conditioning											
Direct Tension Failure Strain, Minimum, 100% Test Temp @ 1.0 min/min, degrees C	-6	-12	-18	-24	-30	0	-6	-12	-18	-24	-30

Section 2 - 34

Asphalt Performance Grading (Example)

- Frontier PG 64-22
- Tested at the Materials office: PG 64-22
- Is it good for Cheyenne at 50% reliability?
- Is it good for Cheyenne at 98% reliability?

Section 2 - 35

PG Asphalt Grade Adjustment

ESALs (million)	Traffic speed		
	>70Km/h	20-70 Km/h	<20 Km/h
<0.3	-	-	-
0.3 to <3	-	1	2
3 to <10	-	1	2
10 to <30	-	1	2
>= 30	1	1	2

70 Km/h =43.5 MPH; 20 Km/h = 12.5 MPH

Section 2 - 36

Performance Grading (Example)

- **Assuming a weigh station will be built near Cheyenne, can you use the Frontier PG64-22 @ 50% reliability?**

- **How about 98% reliability?**

Section 2 - 37

Changing Grade of Binder

- **The grade of asphalt will be specified.**
- **The contractor may use a different grade according with the following (WYDOT 401.2.1)**
 - ▶ **The upper temperature may be increased.**
 - ▶ **The lower temperature may be decreased.**
 - ▶ **The DOT should be notified in writing of any changes before mix production begins.**
 - ▶ **Repeated changing of grades will not be allowed.**

Section 2 - 38
